

Customer: **Shanghai Sheeny Metal Mateirals Co.,Ltd.** P.O.#
Date: **12-Aug-2022** Job #

H0NNM490

Customer ID: **MgO**
MgO2 7-26

Sample ID: **H220808021**

[Rev: 2022-08-23 16:30:18]

Element	Concentration [ppm wt]	Element	Concentration [ppm wt]
Li	0.22	Ag	< 0.5
Be	< 0.05	Cd	< 0.5
B	0.27	In	< 0.5
O	Matrix	Sn	< 0.5
F	< 5	Sb	< 2
Na	0.2	Te	< 0.5
Mg	Matrix	I	< 0.5
Al	0.46	Cs	< 0.5
Si	7.2	Ba	< 0.05
P	1.5	La	< 0.1
S	4.9	Ce	< 0.5
Cl	-	Pr	< 0.1
K	0.06	Nd	< 0.1
Ca	1.2	Sm	< 0.1
Sc	< 0.05	Eu	< 0.1
Ti	< 0.05	Gd	< 0.1
V	2.2	Tb	< 0.1
Cr	1.3	Dy	< 0.1
Mn	1.8	Ho	< 0.1
Fe	2	Er	< 0.1
Co	0.46	Tm	< 0.1
Ni	2.8	Yb	< 0.1
Cu	1.7	Lu	< 0.1
Zn	6.2	Hf	< 0.5
Ga	< 0.1	Ta	Electrode
Ge	< 1	W	< 5
As	< 0.1	Re	< 0.05
Se	< 0.5	Os	< 0.05
Br	< 0.5	Ir	< 0.05
Rb	< 0.05	Pt	< 0.5
Sr	0.35	Au	Interference
Y	< 0.5	Hg	< 0.5
Zr	< 0.5	Tl	< 0.1
Nb	< 20	Pb	1.4
Mo	< 5	Bi	1.1
Ru	< 0.5	Th	< 0.05
Rh	< 0.5	U	< 0.05
Pd	< 0.5		

ISO 17025

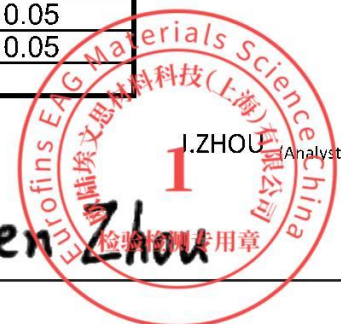


Testing Cert. #2797.04

Page 1 of 1 - GDMS

This report is for reference only and does not serve as a social proof.

Reviewed by

Karen Zhou


Precision and bias typical of GDMS measurements are discussed under ASTM F1593.

This report shall not be reproduced except in full without written approval of the laboratory.

Eurofins EAG Materials Science China does not perform sampling. Analysis was performed on samples and sample locations specified and agreed upon by the client prior to analysis.